


Environmental Certification Scheme

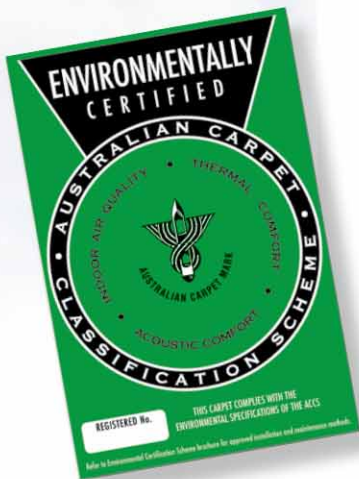

Carpet Name: PD 995-1930
TUNDRA PLAINS
TUNTURI

Licensee: GODFREY HIRST
Licence Number: 1012
Label Number: 21236

Certification Approved: 23/07/2021

Level: 4

ACCS Contract Grading: CMD 2*
ACCS Residential Grading: REHD1 5*
Suitable for Stairs: Yes

Date Printed: 2/08/2021

Allan Firth



Allan Firth
Secretary ACCS



Administered by the Carpet Institute of Australia Limited ABN 11 006 829 303
PO Box 7172, St Kilda Road, Melbourne Victoria 8004 Tel: (03) 9804 5559 • Fax: (03) 9804 5560
Email: info@carpetoz.com.au • www.carpetinstitute.com.au

This certificate remains the property of the Carpet Institute of Australia Limited.

Carpet Details:

Company: GODFREY HIRST

Label No: 21236

Licence No: 1012

Office No: 7183

Names:

PD 995-1930
TUNDRA PLAINS
TUNTURI

Details:

Awarded Res Grade: REHD1 5*
Awarded Con Grade: CMD 2*
Registered On: 23/07/2021
Active: Yes
Date In-Active:
Manufacture Method: Tufted
Twist Set: N/A
Dyeing Method: Loose Fibre
#Colours/Designs: 8
Backing Type: Sec Fabric
Felted: N/A
Spinning System: Woollen
Insect Resist Agent: Eulan SP
Filament: 35
Master Product:

Test Results:

Pile Mass g/m² (oz/yd²): 1085 (32.0)
SPM g/m² (oz/yd²): 648 (19.1)
Stated Pile Height (mm): 3.5
Minimum Pile Height (mm): 0.0
Maximum Pile Height (mm): 0.0
Dynamic Loading Loss (%): 0.0
Static Loading Loss (%): 0.0
Tex (g/1000m): 1200
Measured Pile Thickness (mm): 3.6
Machine Gauge (Tufts/dm): 25.2
Meas Tufts Perp to Selvedge: 25.4
Meas Tufts Para to Selvedge: 24.3
Treated For Soiling Resistance: No
Soil Resist Inhibitor: No
Stain Resist Inhibitor: No

Hexapod Scores:

	Texture		Colour		Thickness	
	WA	WA	WA	WA	(mm)	(%)
1500:	4.0	4.0	4.0	4.0	0.6	16.3
8000:	2.0	2.0	3.0	2.5	1.3	36.1

Quality Assurance Test:

Cut Pile (%): 0
Loop Pile (%): 100
Panel Assessment Contract: 13
Panel Assessment Residential: 13
Suitable For Stairs: Yes
Tile: No SheetGoods: No
Fibre Signature: WOO:100

ACCS Test:

	Con	Res	Max
SPM/PH Ratio:	9.6	13	16
Volume Density:	19.6	19.6	20
Tuft Density:	3.1	3.1	9
Dyn Load:	3.9	3.9	5
Stat Load:	4.1	4.1	5
Soiling Prop:	14	14	16
Abrasion Res:	3.4	3.4	10
Sub Total:	57.7	61.1	81
Panel Assess:	13	13	19
Total:	70.7	74.1	100
Calc Residential Grade:	REHD1	5*	
Calc Contract Grade:	CMD	2*	

Calculations

Pile Height(mm): 4.4
Tuft Density(per dm²): 617.2
GSPM(g/m²): 905.0
GSPM (abrasive) (g/m²): 1320.0
Soiling Propensity: 14.0 +0.0

OAF Values

OAF: 2.8
Calc Density (+-5%): 0.17 0.180 0.19
Base Fibre: WOOL
Benchmarks:
RHD1 0 RHD2 2.7
REHD1 2.7 REHD2 3

Environmental Classification:

ECS: Yes
Level: 4

	Calc	B/M	P/F
Acoustic:	3.6	3	PASS
Thermal:	20	15	PASS
VOC:			
TVOC	93		

Notes:

23/7/21 Submitted by M Chandley. 28/7/21 Panel awarded grading CMD(S) 2*, REHD1(S) 5* and certified ECS Level 4.